arXiv:cond-mat/0601308v1 [cond-mat.mtrl-sci] 16 Jan 2006

Selective dilution and magnetic properties of $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$ (M' = Al, Ti)

D. N. H. Nam,[1,2] L. V. Bau,[1,3,5] N. V. Khiem,[4] N. V. Dai,[1]
L. V. Hong,[1] N. X. Phuc,[1] R. S. Newrock,[2] and P. Nordblad[5]
[1] *Institute of Materials Science, VAST, 18 Hoang-Quoc-Viet, Hanoi, Vietnam*
[2] *Department of Physics, University of Cincinnati, OH 45221-0011, USA*
[3] *Department of Science and Technology, Hongduc University, Thanhhoa, Vietnam*
[4] *Department of Natural Sciences, Hongduc University, Thanhhoa, Vietnam*
[5] *The Ångström Laboratory, Uppsala University, Box 534, SE 751-21 Uppsala, Sweden*
(Dated: February 6, 2008)

The magnetic lattice of mixed-valence Mn ions in $La_{0.7}Sr_{0.3}MnO_3$ is selectively diluted by partial substitution of Mn by Al or Ti. The ferromagnetic transition temperature and the saturation moment decreases with substitution in both series. The volume fraction of the non-ferromagnetic phases evolves non-linearly with the substitution concentration and faster than theoretically expected. By presenting the data in terms of selective dilutions, the reduction of T_c is found to be scaled by the relative ionic concentrations and is consistent with a prediction derived from molecular-field theory.

PACS numbers: 75.10.Hk, 75.30.Cr, 75.30.Et, 75.47.Lx

I. INTRODUCTION

Perovskite manganites with the general composition (R,A)MnO_3 (R: rare earth, A: alkali elements) are attractive to scientists not only because of their potential applications but also due to their very rich and intriguing physics. While most of the pristine compounds $RMnO_3$ are (insulating) antiferromagnets due to antiferromagnetic (AF) superexchange (SE) interactions between Mn^{3+} ions, the introduction of divalent alkali cations such as Sr^{2+}, Ca^{2+}, or Ba^{2+} into the composition converts an adapted number of Mn^{3+} to Mn^{4+} that in turn gives rise to the $Mn^{4+} - O^{2-} - Mn^{3+}$ ferromagnetic (FM) double-exchange (DE)[1] interaction. The presence of DE couplings can turn an insulating antiferromagnetic manganite into a ferromagnet with metallic conductivity. It has been widely accepted that, along with lattice distortions[2,3,4] and phase segregation phenomena,[5] the DE mechanism plays a very important role in governing the properties of manganites.

Perovskite manganites have been intensively studied in the last decade since the discovery of the Colossal Magneto-Resistance (CMR) phenomenon.[6] Chemical substitution has been widely used as a conventional method to uncover the underlying physics and to search for compositions with novel properties. Results for both R- and Mn-site substitution have been quite well documented in the literatures. For manganites with a Mn^{3+}/Mn^{4+} ratio of 7/3, substitution of different elements at the rare-earth site has shown that magnetic and transport properties of many manganites depend rather systematically on the average ionic size, $\langle r_A \rangle = \sum_i y_i r_i$, and the ionic size mismatch defined as $\sigma^2 = \sum_i y_i r_i^2 - \langle r_A \rangle^2$ (where y_i is the fraction and r_i the ionic radius of the ith species occupying the R-site),[4,7] i.e. on the degree of $GdFeO_3$-type lattice distortion and lattice disorder. However, despite many attempts at modifying the magnetic lattice of Mn ions by direct substitution at the Mn-sites, the complexity caused by too many factors that govern the properties of the materials, no universal features have been revealed to date. In this paper, we report that the reduction of the ferromagnetic ordering transition temperature T_c of $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$ (M' = Al, Ti) scales with the relative substitution concentrations and is consistent with a prediction from molecular-field theory (MFT) of the dilution of a magnetic lattice. The substitutions with Al and Ti are *selective* in nature because Al^{3+} only substitutes for Mn^{3+} and Ti^{4+} only for Mn^{4+}. Another advantage of these substitutions is that because Al^{3+} and Ti^{4+} ions do not carry a magnetic moment, they are also expected not to participate in the magnetic interaction.

II. EXPERIMENT

In this paper, $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$ is denoted as $LSMA_x$ for M' = Al and $LSMT_x$ for M' = Ti. All the samples were prepared using a conventional solid state reaction method. Pure ($\geq$99.99%) raw powders with appropriate amounts of La_2O_3, $SrCO_3$, MnO_2, Al_2O_3, and TiO_2 are thoroughly ground, mixed, pressed into pellets and then calcined at several processing steps with increasing temperatures from 900 °C to 1200 °C and with intermediate grindings and pelletizations. The products are then sintered at 1370 °C for 48 h in ambient atmosphere. The final samples are obtained after a very slow cooling process from the sintering to room temperature with an annealing step at 700 °C for few hours. Room-temperature X-ray diffraction patterns (measured by a SIEMENS-D5000 with Cu-K_α radiation) show that all of the samples are crystallized in perovskite rhombohedral structures with almost no sign of secondary phases or remnants of the starting materials. The crystal structures obtained for the samples are in agreement with earlier structural studies.[8,9,10,11,12] Transport and magnetotransport measurements were carried out in a non-commercial cryostat using the standard 4-probe method.

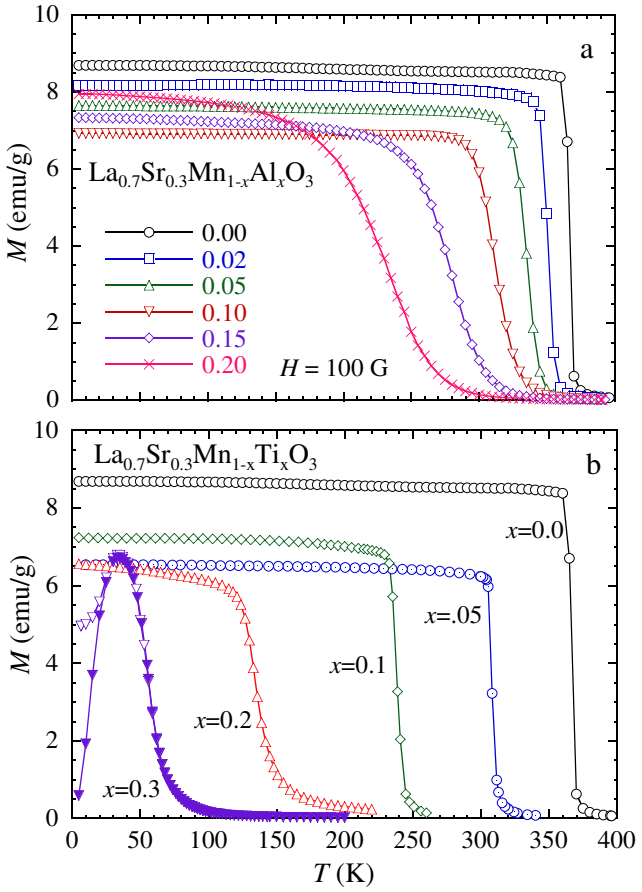

FIG. 1: Field-cooled magnetization as a function of temperature for (a) $La_{0.7}Sr_{0.3}Mn_{1-x}Al_xO_3$ and (b) $La_{0.7}Sr_{0.3}Mn_{1-x}Ti_xO_3$, measured in $H = 100$ G. The zero-field-cooled $M_{ZFC}(T)$ (▼) of the $x = 0.3$ sample is added for further discussions.

Magnetic and magnetization measurements were performed in a Quantum Design MPMS SQUID magnetometer and (sometimes) by a Vibrating Sample Magnetometer (VSM).

III. RESULTS AND DISCUSSION

Magnetic, transport, and magnetotransport characterization of $LSMA_x$ and $LSMT_x$ compounds has been reported previously by other authors and can be referenced in a number of publications.[8,9,10,11,12,13] Although consistent tendencies as to the variation of e.g. the transition temperature and saturation moment with doping concentration have been found, there is significant scatter in the data in-between the different studies. In the current work, the essential characteristics are carefully measured and reexamined.

A. Temperature dependent characterization

Temperature dependent magnetization measurements, $M(T)$, in both zero-field-cooled (ZFC) and field-cooled (FC) protocols, are carried out for all the samples. The FC $M(T)$ curves presented in Fig. 1 clearly indicate that the substitution of Al or Ti for Mn causes the ferromagnetic-paramagnetic (PM) transition temperature T_c to drop drastically. The reduction of T_c in the case of Ti substitution is much more substantial. The FM-PM transition is very sharp at small x concentrations for both doping series but becomes broader with increasing x. A transition is observed for all the samples, even with $LSMT_{0.3}$ where Mn^{4+} ions are supposed to be completely absent. However, as is implied by the ZFC and FC $M(T)$ curves in Fig. 1, the $LSTMT_{0.3}$ sample is not a true ferromagnet, nor a pure spin glass as has been suggested in Ref. 12 for this composition. This last conclusion is also corroborated by the fact that our frequency-dependent ac-susceptibility measurements $\chi_{ac}(T,\omega)$ (not shown) do not indicate a dynamic phase transition. The $M(T)$ curves for this sample probably suggest the existence of an AF background state with a weak ferromagnetic component — possible indications of a canted antiferromagnet, as was proposed in Ref. 10. The T_c vs. x data extracted from the $M(T)$ curves for all samples are plotted in Fig. 4 and will be discussed later in detail.

Temperature dependent transport measurements for both series show that the resistivity, ρ, strongly increases with increasing x while the metal-insulator (MI) transition usually observed at a temperature T_p near (but lower than) T_c is shifted to lower temperatures. The MI transition is observed in all of the $LSMA_x$ samples while it can only be observed in $LSMT_x$ for x up to 0.1. For $LSMT_{0.2}$, the MI transition is no longer observed, but there still exists a slope change in the $\rho(T)$ curve at a temperature below T_c signalling a magnetic contribution from the FM phase to the conductivity. In agreement with the magnetic behavior, the $LSMT_{0.3}$ sample only shows insulating characteristics.

B. Magnetization characterization

The theoretical zero-temperature spin-only saturation magnetization (in emu/g) of the $LSMA_x$ and $LSMT_x$ compounds follow

$$M_s = \begin{cases} (3.7-4x)10^3/(40.548-5.006x) & \text{if } M' = \text{Al} \\ (3.7-3x)10^3/(40.548-1.801x) & \text{if } M' = \text{Ti.} \end{cases} \quad (1)$$

For the $LSMA_x$ series, magnetization measurements at $T = 5$ K (the inset of Fig. 2) indicate that the samples are substantially saturated in an applied field of just above 1 T. At higher fields, the $LSMA_0$ and $LSMA_{0.05}$ samples exhibit flat $M(H)$ dependencies as expected for conventional ferromagnets at high fields and low temperatures. Closer inspection on the $M(H)$ curves for

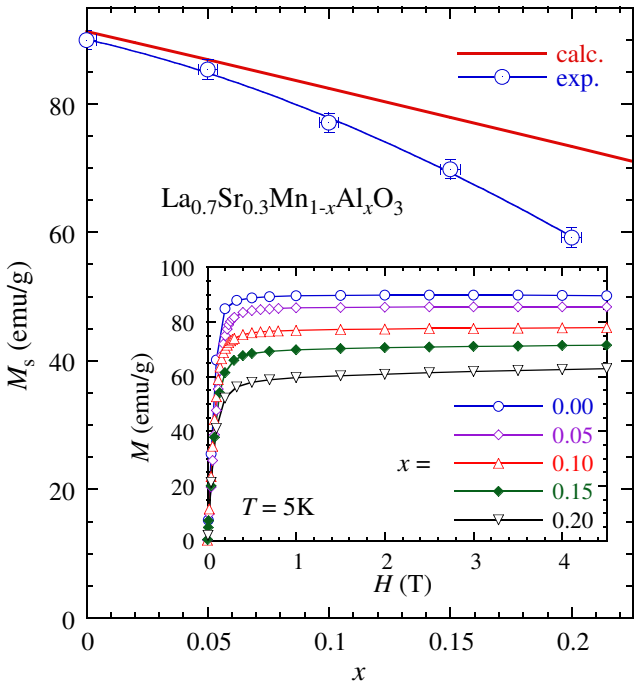

FIG. 2: $La_{0.7}Sr_{0.3}Mn_{1-x}Al_xO_3$: Theoretical M_s vs. x calculated from equation 1 (bold curve without symbols) and experimental M_s data (thin curve with $\odot$ symbols) extracted from $M(H)$ measurements at 5 K (inset).

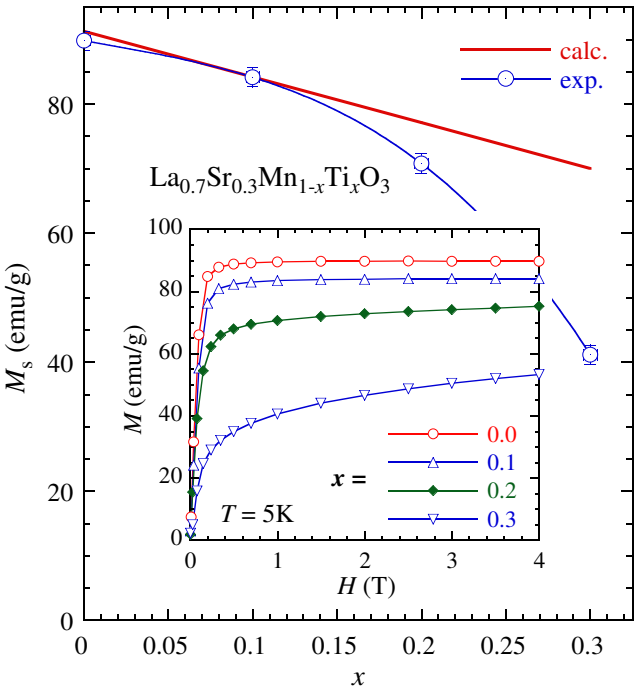

FIG. 3: $La_{0.7}Sr_{0.3}Mn_{1-x}Ti_xO_3$: Theoretical M_s vs. x calculated from equation 1 (bold curve without symbols) and experimental M_s data (thin curve with $\odot$ symbols) extracted from $M(H)$ measurements at 5 K (inset).

$x \geq 0.1$ shows, however, that they are quite linear in the high-field regime up to 4.5 T with a small slope which increases with x. The small slope would come from the suppression of thermal fluctuations of the magnetization by the magnetic field. However, the evolution of the slope of the $M(H)$ curves with x in the high field regime may signal a magnetic contribution from certain Mn ions that do not take part in the ferromagnetic phase. In addition, for the whole series, the measured magnetization in magnetic fields up to 4.5 T does not reach the theoretical magnetization value and even deviates further with increasing x. Based on these features, it is presumable that segregation into FM and non-FM phases occurs in these samples. The experimental values of the saturation magnetization M_s of the FM phase presented in Fig. 2 (and also Fig. 3 for Ti substitution) are determined by extrapolating the linear part of the $M(H)$ curves in the high field regime to $H = 0$. The difference between experimental and theoretical M_s is then attributed to the non-FM contributions, $M_{\mathrm{non-FM}}$.

Very similar results are also obtained for the $LSMT_x$ series, as can be seen in Fig. 3. Previous observations of the decrease of M_s in Al and Ti substitutions in manganites have been published and interpreted by several other authors.[10,11,12,14,15] The decrease of M_s was attributed to the dilution and the weakening of FM exchange couplings as in general. Kallel *et al.*[10] suggest even a change of the spin state or the orbital ordering of the Mn ions. The deviation between the experimental M_s and its theoretical values has not been adequately considered. In a study on $La_{0.7}Ca_{0.3}Mn_{1-x}Al_xO_3$ by neutron diffraction, the effective magnetic moment per Mn ion was found far smaller than the saturation moment and that was explained by assumptions of magnetic inhomogeneity and structural disorder.[14] Our interpretation for the M_s deviation in terms of magnetic phase segregation is somehow closer to that proposed for $La_{0.7}Ca_{0.3}Mn_{1-x}M'_xO_3$ (M'= Ti, Ga) compounds by Cao *et al.*,[15] where the authors suggest that Ti^{4+} and Ga^{3+} ions generate around them non-ferromagnetic (paramagnetic or possibly antiferromagnetic) regions.

As pointed out above, there is a growing deviation of the FM saturation magnetization from the calculated value with increasing substitution concentration. This observation indicates that the substitution not only reduces the total number of Mn ions but also raises the number of non-FM Mn ions at the expense of the FM phase. Since the Mn^{3+}/Mn^{4+} ionic concentration ratio is driven away from the optimal value of 7/3 by the substitution, a certain amount of the Mn ions may become *redundant* with respect to the DE couplings. I.e., the selective substitution on one Mn ionic species produces the redundancy on the other Mn species. Those redundant ions contribute to the non-FM phase. With small values of x, the redundant ions are thus mostly Mn^{4+} for $M' =$ Al while they are Mn^{3+} for the Ti substitution. Based on this assumption the concentration of non-FM Mn ions can approximately be derived from $M_{\mathrm{non-FM}}$.

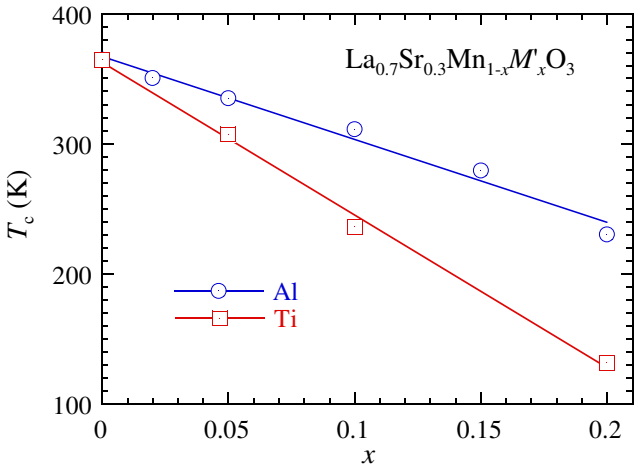

FIG. 4: $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$: Variation of T_c with substitution concentration x ($0 \le x \le 0.2$) for M' = Al ($\odot$) and Ti ($\boxdot$).

For examples, with $x = 0.2$, the estimated redundant concentration of Mn^{4+} is 0.187 for M' = Al and the corresponding concentration of Mn^{3+} is 0.064 for M' = Ti. With sufficiently high substitution concentrations, contributions to the the non-FM phase may also arise from the Mn ions of both species that are isolated by the nonmagnetic ones.

C. Effects of selective dilution and the MFT approximation

Figure 4 shows the dependence of the FM-PM phase transition temperature T_c on substitution concentration, derived from the low-field $M(T)$ data in Fig. 1. The T_c values are determined by the temperatures at which the $\partial M/\partial T$ curves peak. The parent compound, $La_{0.7}Sr_{0.3}MnO_3$, has T_c = 364.4 K, in good agreement with previously reported data.[16] T_c decreases monotonically as x increases in both cases. Explanations for the decrease of T_c with Al and Ti substitution in manganites have been suggested by several authors.[8,10,11,13] One explanation is simply that the decrease of T_c is due to the suppression of long-range FM order of the localized t_{2g} spins by local breakdown of the exchange couplings where the substitution occurs.[8,13] Hu *et al.*[9] assumed that the substituted Ti^{4+} ions tends to demolish the DE $Mn^{3+} - O^{2-} - Mn^{4+}$ bonds and lowers the hole carrier concentration, thus suppressing the DE interaction and lowering T_c. Kallel *et al.*[10] suggested that the presence of Ti in $LSMT_x$ favors SE interaction and suppresses the DE mechanism. Significantly, Kim *et al.*[11] recently found that the Ti substitution in $LSMT_x$ increases the $Mn - O - Mn$ bond length and reduces the bond angle. Based on structural data, the authors calculated the variation of e_g-electron bandwidth W, finding a decrease of W with x, and related it to the decrease of T_c. It is worth noting that the ionic size of Mn^{4+} (0.530 Å) is smaller than that of Ti^{4+} (0.605 Å) while Mn^{3+} (0.645 Å) is larger than Al^{3+} (0.535 Å).[17] As a result, the effects of Al and Ti substitution on the structure, and hence W, may not be the same and even opposite in the two cases. However, in reality, T_c has been found always to decrease with the substitution. A detailed study on the structure of $LSMA_x$ may help justify the cause.

As is seen in Fig. 4, the effect of substitution with Ti on the reduction of T_c (defined by $\Delta T_c = T_c(x) - T_c(0)$) is as much as more than twice of that of Al substitution. However, as mentioned above, because the substitution is selective, in order to compare their effects, instead of using x as the common variable, the data should be presented as functions of relative substitution concentrations, defined as $n_p = x/0.7$ when M' = Al and $n_p = x/0.3$ when M' = Ti. Physically, n_p is the average concentration of M' per Mn site of the selectively-substituted Mn ionic species (Mn^{3+} for M' = Al, or Mn^{4+} for M' = Ti), or the probability that site is occupied by an M' ion. Strikingly, as displayed in Figure 5, the $T_c(n_p)$ data for M' = Al and Ti collapse onto one curve which follows very well the linear line predicted by the molecular-field theory (see below). It is also surprising that the linear behavior of $T_c(n_p)$ of $LSMT_x$ sustains in a very wide range of n_p and has the tendency to reduce to zero at $n_p = 1$.

For further understanding and analyzes of the results, we use a mean-field approximation to derive the relation between T_c and n_p. According to the Heisenberg model, the potential energy of exchange interactions of any particular magnetic ion i with the other ions j is given by $U_i = -2S_i \cdot \sum_{j \ne i} J_{ij} S_j$ where S_i, S_j are the spins of the ith and jth ions respectively; and J_{ij} the exchange integral. U_i can be rewritten as

$$U_i = -2\frac{\mu_i}{g^2} \cdot \sum_{j \ne i} J_{ij}\mu_j = -2\frac{\mu_i \cdot M}{Ng^2} \sum_{j \ne i} J_{ij} \qquad (2)$$

where M and N are the magnetic moment and the number of magnetic ions per unit volume, respectively and μ_i, μ_j are the magnetic moment of the ith and jth ions. For simplicity, μ_j is replaced with the average magnetic moment per site $\langle\mu\rangle = \frac{M}{N}$. Assuming that the ith ion interacts only with its nearest-neighbor ions, but with n different exchange coupling constants $J_{i\alpha}$ each involves $z_{i\alpha}$ ions, then instead of summing over the ions j, the summation is made over the interactions. We can then recast Eq. 2 as

$$U_i = -2\frac{\mu_i \cdot M}{Ng^2} \sum_{\alpha}^{n} z_{i\alpha} J_{i\alpha}. \qquad (3)$$

According to the MFT, $U_i = -\mu_i \cdot B_M = -\mu_i \cdot \lambda M$ and $T_c = \lambda C$, where B_M is the molecular field, and C and λ are, respectively, the Curie and Weiss constants, Eq. 3 becomes

$$T_c = \frac{2S_i\,(S_i+1)}{3k_B} \sum_{\alpha}^{n} z_{i\alpha} J_{i\alpha}. \qquad (4)$$

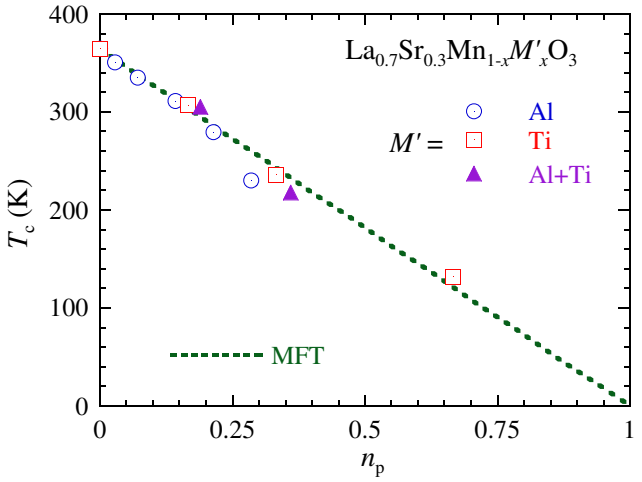

FIG. 5: $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$: T_c is presented as a function of relative concentration $n_p = x/0.7$ for $M' =$ Al ($\odot$) or $n_p = x/0.3$ for $M' =$ Ti ($\boxdot$). The broken line presents a prediction from molecular-field theory. The data for $La_{0.7}Sr_{0.3}Mn_{0.9}Al_{0.07}Ti_{0.03}O_3$ ($n_p = 0.19$) and $La_{0.7}Sr_{0.3}Mn_{0.8}Al_{0.14}Ti_{0.06}O_3$ ($n_p = 0.36$) ($\blacktriangle$) are added for further discussions (see text for details).

For a simple system where there is only one species of magnetic ion and hence one kind of exchange interaction, Eq. 4 equals the standard expression

$$T_c = \frac{2S(S+1)zJ}{3k_B}. \quad (5)$$

When the system is diluted by a substituting nonmagnetic element, and if the substitution is completely random with respect to its lattice site, the dilution would result in a proportional dependence $z(n_p) = z(0)(1-n_p)$ where $0 \le n_p \le 1$ and $z(0)$ refers to the undiluted system. Replacing $z(n_p)$ for z in Eq. 5 yields a linear dependence of T_c on n_p as illustrated in Figure 5.

Nevertheless, Eq. 5 is perhaps not relevant to our manganite systems at first because of the mixed-valence of the Mn ions and the coexistence of different kinds of interaction including SE AF interactions $Mn^{3+} - O^{2-} - Mn^{3+}$, $Mn^{4+} - O^{2-} - Mn^{4+}$, and the DE FM interaction $Mn^{3+} - O^{2-} - Mn^{4+}$ with corresponding exchange constants denoted as J_{SE1}, J_{SE2}, and J_{DE}, and nearest-neighbor interacting ions number z_{SE1}, z_{SE2}, and z_{DE}, respectively. According to Eq. 4, a linear behavior is expected to be observed for $T_c(n_p)$ only if (i) the exchange coupling constants are unchanged and (ii) the dilution either affects $z_{i\alpha}$ in a proportional manner such that $z_{i\alpha}(n_p) \propto (1-n_p)z_{i\alpha}(0)$ or does not affect it at all. Supposing that J_{DE}, J_{SE1}, J_{SE2} do not change with substitution, within the linearity regime of $T_c(n_p)$, it is presumable that the Al (or Ti) substitution leaves z_{SE2} (or z_{SE1}) intact but possibly changes both z_{DE} and z_{SE1} (or z_{SE2}) proportionally to $1-n_p$. The most remarkable feature of the $T_c(n_p)$ variation in Fig. 5 is that T_c has a tendency to go to zero when $n_p = 1$. This would simply mean that the zJ product of DE couplings is totally dominant over those of the SE ones. Considering the fact that at low dilution concentrations, since the Mn^{3+} and Mn^{4+} concentrations are not too different, z_{DE}, z_{SE1}, and z_{SE2} are possibly comparable, thus it is reasonable to suppose that the SE couplings J_{SE1}, J_{SE2} both are negligibly small in these systems. This could be one reason behind the fact that $La_{0.7}Sr_{0.3}MnO_3$ is a unique manganite in the sense that it has the highest T_c amongst the perovskite manganites. In a situation when the SE coupling constants are significant, because either z_{SE1} or z_{SE2} does not change by selective substitution, according to Eq. 4, $T_c(n_p)$ may still have a linear dependence but should have a tendency to intercept n_p-axis at a certain value $n_p < 1$.

Apart from changes of the z values, the substitution of Al or Ti for Mn could cause some additional effects. Because they are nonmagnetic, the magnetic coupling will be broken at any site they occupy, leading to a weakening of long-range FM ordering established by the dominant DE interactions and a deterioration of the metallic conductivity. The selectivity of the substitution also drives the Mn^{3+}/Mn^{4+} ratio away from the optimal 7/3 value contributing to developing the non-FM phase. The differences in ionic sizes between Mn and Al and Ti could modify the crystal structure, especially the angle and length of the $Mn-O-Mn$ couplings.[18] All these factors contribute to the degradation of the ferromagnetism and metallicity of the manganite system. Nevertheless, the linear behavior of $T_c(n_p)$ observed in Fig. 5 implies that, within the substitution ranges, those effects are dominated by the effect of dilution. In addition, there is a significant difference between the two substitutions. While the amount of Al substitution reduces the number of hopping electrons by an equivalent amount, Ti substitution does not affect it at all. The shortage of hopping electrons would possibly explain the large number of Mn^{4+} redundancy in the $LSMA_x$ compounds. We believe that this difference has a link to the reason why the linear behavior of $T_c(n_p)$ of $LSMA_x$ occurs in a much narrower range of dilution ($n_p \le 0.25$) than that of $LSMT_x$ where $T_c(n_p)$ is found linear up to $n_p = 0.67$. It is worth noting that $T_c(n_p)$ would not follow the linear behavior up to $n_p = 1$ as predicted by the MFT because there should exist a percolation threshold n_c, above which clustering occurs and the ferromagnetic network collapses into only short-range ordering and superparamagnetism.

In the case when both Al and Ti are substituted for Mn with according n_p(Al) and n_p(Ti), supposing that the ferromagnetic double exchange is totally dominant in the system, the dilution concentration of the whole system is determined as $n_p = 1-(1-n_p(\text{Al}))(1-n_p(\text{Ti}))$. To check the validity of the MFT analysis in this case, the $T_c(n_p)$ values of the $La_{0.7}Sr_{0.3}Mn_{0.9}Al_{0.07}Ti_{0.03}O_3$ ($n_p = 0.19$) and $La_{0.7}Sr_{0.3}Mn_{0.8}Al_{0.14}Ti_{0.06}O_3$ ($n_p = 0.36$) compounds are also added to Figure 5. The data fit fairly well the MFT prediction. However, when the

superexchange interactions are taken into account, the physical scenario for this case will be more complicated and may need further detailed investigations.

IV. CONCLUSION

We have reexamined the magnetic and transport properties of the $La_{0.7}Sr_{0.3}Mn_{1-x}M'_xO_3$ system, where Mn is selectively substituted by M' = Al or Ti; either Mn^{3+} or Mn^{4+} is selectively substituted for, but M' is randomly distributed in the Mn network. The analyzes of the $M(H)$ measurements and saturation magnetization revealed that the substitution appears to not only merely dilute the magnetic lattice of Mn ions, but also induce a redundancy of Mn ions. We have introduced the *selective dilution concentration* n_p and discovered that in certain ranges of n_p, depending on particular M', T_c scales very well with n_p in linearity, being in good agreement with the MFT approximation. The tendency of T_c to reduce to zero at $n_p = 1$ suggests a dominant role of the DE mechanism in this system; the SE interaction is effectively negligible. Remarkably, the linear behavior of $T_c(n_p)$ is observed in a very wide range of n_p in $LSMT_x$ making this system an excellent candidate for studies on the effects of dilution where T_c could be almost independently tuned without side effects. It is also proposed that the reduction in the number of hopping e_g electrons is one cause for the difference in the effects of dilution between the $LSMT_x$ and $LSMA_x$ compounds. The MFT analyzes are found to some extend also valid for the case when Al and Ti are both substituted for Mn.

Acknowledgments

This work has been performed partly under the sponsorship of a collaborative project between the Institute of Materials Science (VAST, Vietnam) and Uppsala University (Sweden). Two of us would like to thank the University of Cincinnati and the National Science Foundation for support. Dr. L. V. Bau would like to acknowledge the financial support from the Ph.D Training Program of the Ministry of Education and Training of Vietnam, and is in debt to the collaboration and training project between the IMS and Hongduc University.

[1] C. Zener, Phys. Rev. **82**, 403 (1951).
[2] A. J. Millis, P. B. Littlewood, and B. I. Shraiman, Phys. Rev. Lett. **74**, 5144 (1995).
[3] A. J. Millis, R. Mueller, B. I. Shraiman, Phys. Rev. Lett. **77**, 175 (1996).
[4] H. Y. Hwang, S. W. Cheong, P. G. Radaelli, M. Marezio, and B. Batlogg, Phys. Rev. Lett. **75**, 914 (1995).
[5] E. Dagotto, T. Hotta, and A. Moreo, Phys. Rep. **344**, 1 (2001).
[6] R. V. Helmolt, J. Wecker, B. Holzapfel, L. Schultz, and K. Samwer, Phys. Rev. Lett. **71**, 2331 (1993).
[7] J. M. de Teresa, M. R. Ibarra, J. García, J. Blasco, C. Ritter, P. A. Algarabel, C. Marquina, and A. del Moral, Phys. Rev. Lett. 76, 3392 (1996).
[8] H. Qin, J. Hu, J. Chen, H. Niu, and L. Zhu, J. Magn. Magn. Mater. **263**, 249 (2003).
[9] J. Hu, H. Qin, J. Chen, and Z. Wang, Mater. Sci. Eng. B **90**, 146 (2002).
[10] N. Kallel, G. Dezanneau, J. Dhahri, M. Oumezzine, and H. Vincent, J. Magn. Magn. Mater. **261**, 56 (2003).
[11] M. S. Kim, J. B. Yang, Q. Cai, X. D. Zhou, W. J. James, W. B. Yelon, P. E. Parris, D. Buddhikot, and S. K. Malik, Phys. Rev. B **71**, 014433 (2005).
[12] I. O. Troyanchuk, M. V. Bushinsky, H. Szymczak, K. Bärner, and A. Maignan, Eur. Phys. J. B **28**, 75 (2002).
[13] Y. Sawaki, K. Takenaka, A. Osuka, R. Shiozaki, and S. Sugai, Phys. Rev. B **61**, 11588 (2000).
[14] J. Blasco, J. García, J. M. de Teresa, M. R. Ibarra, J. Perez, P. A. Algarabel, and C. Marquina, Phys. Rev. B **55**, 8905 (1997).
[15] D. Cao, F. Bridges, M. Anderson, A. P. Ramirez, M. Olapinski, M. A. Subramanian, C. H. Booth, and G. H. Kwei, Phys. Rev. B **64**, 184409 (2001).
[16] J. M. D. Coey, M. Viret, and S. von Molnár, Adv. Phys. **48**, 167 (1999).
[17] R. D. Shannon, Acta Cryst. A **32**, 751 (1976).
[18] J. L. García-Muñoz, J. Fontcuberta, M. Suaaidi, and X. Obradors, J. Phys.: Condens. Matter **8**, L787 (1996).